

Possible high temperature superconductivity in Ti-doped A-Sc-Fe-As-O (A= Ca, Sr) system

G. F. Chen^{1,2}, T. -L. Xia², H. X. Yang¹, J. Q. Li¹, P. Zheng¹, J. L. Luo¹, and N. L. Wang¹

¹*Beijing National Laboratory for Condensed Matter Physics,*

Institute of Physics, Chinese Academy of Sciences,

Beijing 100190, Peoples Republic of China and

²*Department of Physics, Renmin University of China,*

Beijing 100872, People's Republic of China

Abstract

We report a systematic study on the effect of partial substitution of Sc^{3+} by Ti^{4+} in $\text{Sr}_2\text{ScFeAsO}_3$, $\text{Ca}_2\text{ScFeAsO}_3$ and $\text{Sr}_3\text{Sc}_2\text{Fe}_2\text{As}_2\text{O}_5$ on their electrical properties. High level of doping results in an increased carrier concentration and leads to the appearance of superconductivity with the onset of T_c up to 45 K.

PACS numbers: 74.70.-b, 74.25.Gz, 74.25.Fy

Since the discovery of superconductivity in $\text{LaFeAsO}_{1-x}\text{F}_x$ (abbreviated as 1111) with $T_c \sim 26$ K,[1] the FeAs-based systems have attracted a great deal of research interest. Substituting La with other rare earth (RE) elements with smaller ion radii dramatically enhances the T_c up to 41-55 K.[2, 3] At room temperature, all these parent compounds crystallize in a tetragonal ZrCuSiAs -type structure, which consists of alternate stacking of edge-sharing Fe_2As_2 tetrahedral layers and RE_2O_2 tetrahedral layers along c-axis. Soon after this discovery, another group of compounds AFe_2As_2 ($\text{A}=\text{Ba}, \text{Sr}, \text{Ca}$) (122), which crystallize in a tetragonal ThCr_2Si_2 -type structure with identical Fe_2As_2 tetrahedral layers as in LaFeAsO , were also found to be superconducting with T_c up to 38 K upon hole doping.[4, 5, 6] Except for the above systematically studied series of iron-based superconductors, attempts have also been tried to find iron-based superconductors with new structures, resulting in the discovery of superconductors like A_xFeAs ($\text{A}=\text{Li}, \text{Na}$)[7, 8, 9] and $\text{FeSe}_{1-x}\text{Te}_x$. [10]

On the other hand, it seems that critical temperature increases with increasing the length of separation between the two neighboring $\text{Fe}(\text{As}, \text{P})$ layers.[11] Indeed, $\text{Sr}_2\text{ScFePO}_3$ (21113) have been reported to be superconducting with T_c up to 17 K, which is the highest in arsenic-free iron-based oxypnictide systems.[12] The same structure was previously studied in oxypnictides and oxychalcogenide systems,[13, 14, 15] where superconductivity have been predicted to be existing once the carries are appropriately introduced into the systems. The crystal structure of such materials constitutes of one perovskite-like $\text{Sr}_4\text{Sc}_2\text{O}_6$ layer alternating with an edge-sharing Fe_2P_2 tetrahedral layer along c-axis. Hence the expanded c-axis lattice constant makes it a good candidate for high temperature superconductors. In such materials, doping can be applied at Sr/Sc/O sites within the perovskite-like units and the Fe_2P_2 layers as well. To search for the superconductors with higher critical temperature, we have also tried different materials with stacking structure of perovskite-type oxide layer and anti-fluorite pnictide layer in oxypnictides. In present work, we report on successful preparation of $\text{A}_2\text{ScFeAsO}_3$ ($\text{A}=\text{Ca}, \text{Sr}$) and a systematic study on effect of partial substitution of Sc^{3+} by Ti^{4+} in $\text{A}_2\text{ScFeAsO}_3$ and $\text{Sr}_3\text{Sc}_2\text{Fe}_2\text{As}_2\text{O}_5$ (32225) on the electrical properties. Substituting Sc^{3+} by Ti^{4+} results in an increased carrier concentration and leads to the appearance of superconductivity with a possible critical temperature as high as 45 K.

The polycrystalline samples were prepared by the solid state reaction method using SrAs, CaAs, SrO, CaO, Sc_2O_3 , TiO_2 , Fe, FeAs and Fe_2As as starting materials. SrAs and CaAs were obtained by reacting Sr or Ca and As at 800°C for 20 h. FeAs and Fe_2As were pre-

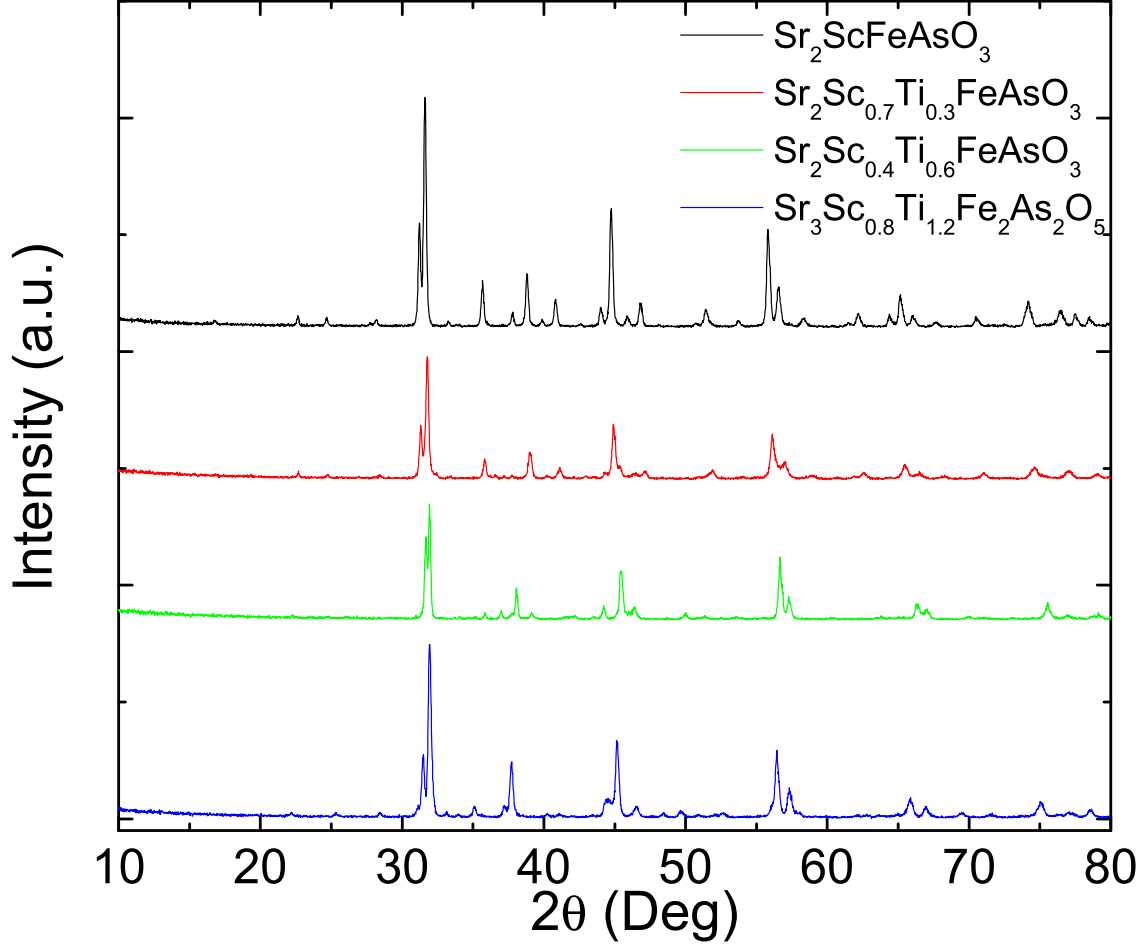


FIG. 1: (Color online) X-ray powder diffraction patterns for $\text{Sr}_2\text{Sc}_{1-x}\text{Ti}_x\text{FeAsO}_3$ ($x=0, 0.3, 0.6$) and $\text{Sr}_3\text{Sc}_{0.8}\text{Ti}_{1.2}\text{Fe}_2\text{As}_2\text{O}_5$.

pared by reacting Fe and As at 900°C for 20 h. All the powders were weighed in a desired ratio and the mixtures were ground thoroughly and cold-pressed into pellets. The pellets were sealed in quartz tube under argon atmosphere. They were then annealed for 50 h at a temperature of 1150°C . The resulting samples were characterized by a powder X-ray diffraction(XRD) method with Cu $K\alpha$ radiation at room temperature. The electrical resistivity measurements were performed in a Physical Property Measurement System(PPMS) of Quantum Design company with standard 4-probe method. The electron diffraction pattern and high-resolution image were obtained on a FEI Tecnai-F20 (200 kV) transmission electron microscope (TEM). The TEM samples were prepared by crushing the polycrystalline parent compound, then the resultant suspensions were dispersed on a holy carbon-covered Cu grid.

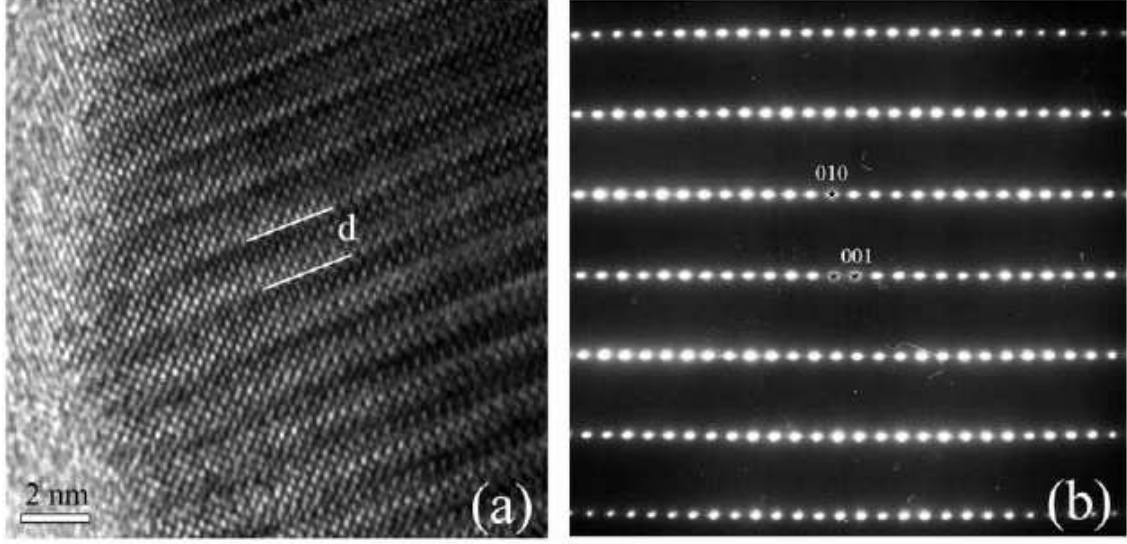


FIG. 2: (Color online) High-resolution TEM image (a) and corresponding electron diffraction pattern (b) of a $\text{Sr}_2\text{ScFeAsO}_3$ crystal viewed along the $[100]$ zone axis direction.

XRD patterns for $\text{Sr}_2\text{Sc}_{1-x}\text{Ti}_x\text{FeAsO}_3$ ($x=0, 0.3, 0.6$) and $\text{Sr}_3\text{Sc}_{0.8}\text{Ti}_{1.2}\text{Fe}_2\text{As}_2\text{O}_5$ are shown in Fig.1. For $\text{Sr}_2\text{ScFeAsO}_3$ and $\text{Sr}_2\text{Sc}_{0.7}\text{Ti}_{0.3}\text{FeAsO}_3$, all the main peaks can be indexed on the basis of tetragonal $\text{Sr}_2\text{FeCuSO}_3$ -type structure with the space group P4/nmmz . The lattice constants for the parent compound were determined to be $a = 4.048 \text{ \AA}$ and $c = 15.804 \text{ \AA}$. However, the high level of doping tends to be more favorable for the formation of $\text{Sr}_3\text{Sc}_{2-x}\text{Ti}_x\text{Fe}_2\text{As}_2\text{O}_5$ with the space group of I4/mmm . For comparison, we display also the diffraction pattern of the sample $\text{Sr}_3\text{Sc}_{0.8}\text{Ti}_{1.2}\text{Fe}_2\text{As}_2\text{O}_5$, which was prepared under the same conditions.

Figure 2 shows the typical high-resolution TEM image and corresponding electron diffraction pattern of the as synthesized product viewed along the $[100]$ zone axis direction. All the diffraction spots shown in Fig. 2(b) can be well indexed by the space group P4/nmm with $b \sim 4.0 \text{ \AA}$ and $c \sim 16 \text{ \AA}$, which coincide well with corresponding values obtained from XRD patterns. In addition, the high-resolution image taken along the $[100]$ zone axis shows clear layered structure with the layer distance d of about $16 \text{ \AA}$, which is in good agreement with the c -axis lattice parameter determined by X-ray diffraction measurement. As a result, we can confirm that the sample used in the present TEM study is $\text{Sr}_2\text{ScFeAsO}_3$ phase. Due to the different space groups and lattice parameters between 21113 phase (P4/nmm) and 32225 phase (I4/mmm), they exhibit different electron diffraction pattern along the $[100]$

zone axis.

Figure 3(a) shows the temperature dependence of the resistivity for $\text{Sr}_2\text{ScFeAsO}_3$. The parent compound exhibits a semiconducting-like behavior. No obvious anomaly is observed in resistivity. This is in contrast to those of the three prototype parent compounds with ZrCuSiAs -, ThCr_2Si_2 - and PbFCl -type structures, in which strong anomalies related to structural/magnetic phase transitions occur in the parent compounds. Electron- or hole-doping strongly weakens this anomaly and induces superconductivity. The existence of competing orders are the common feature for those compounds and high temperature superconductivity appears near this instability. Figure 3(b) shows the temperature dependence of the resistivity for a series of $\text{Sr}_2\text{Sc}_{1-x}\text{Ti}_x\text{FeAsO}_3$ with $x=0.2-0.8$. With the Ti^{4+} -doping, the

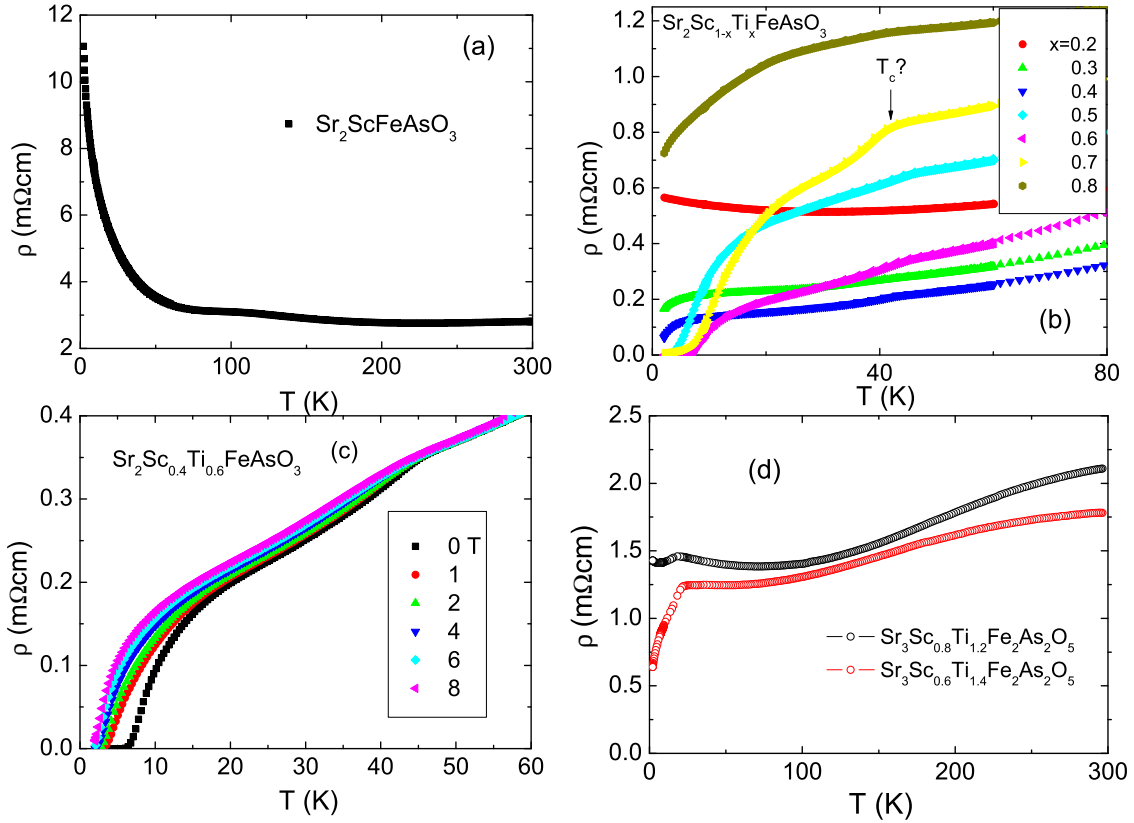


FIG. 3: (Color online) (a) The electrical resistivity vs temperature for the parent compound $\text{Sr}_2\text{ScFeAsO}_3$. (b) The electrical resistivity vs temperature for a series of $\text{Sr}_2\text{Sc}_{1-x}\text{Ti}_x\text{FeAsO}_3$ ($x=0.2-0.8$). (c) The electrical resistivity vs temperature for $\text{Sr}_2\text{Sc}_{0.4}\text{Ti}_{0.6}\text{FeAsO}_3$ in magnetic fields up to 8 T. (d) The electrical resistivity vs temperature for $\text{Sr}_3\text{Sc}_{2-x}\text{Ti}_x\text{Fe}_2\text{As}_2\text{O}_5$ with $x=1.2$ and 1.4 .

resistivity decreases and shows a metallic behavior. It superconducts when it is doped with 30% Ti on Sc sites. While the onset of superconductivity occurs at about 45 K, full bulk superconductivity is observed until 7 K for the sample of $\text{Sr}_2\text{Sc}_{0.4}\text{Ti}_{0.6}\text{FeAsO}_3$. The two step-like phenomena in conductivity may originate from two different superconducting phases. Figure 3(c) shows the resistivity of $\text{Sr}_2\text{Sc}_{0.4}\text{Ti}_{0.6}\text{FeAsO}_3$ in magnetic fields up to 8 T. The superconductivity was suppressed slowly by applying the magnetic fields, indicating the superconductivity is intrinsic. It is difficult to determine the upper critical fields due to the broad transition. It is rather interesting that $\text{Sr}_2\text{Sc}_{1-x}\text{Ti}_x\text{FeAsO}_3$ does superconduct even for the high level of doping with $x=0.7$. As mentioned above, the high level of doping possibly leads to the formation of “32225” phase. Hence we attempted to dope $\text{Sr}_3\text{Sc}_2\text{Fe}_2\text{As}_2\text{O}_5$ with the same route. A trace of superconductivity extending up to near 20 K was observed in $\text{Sr}_3\text{Sc}_{0.8}\text{Ti}_{1.2}\text{Fe}_2\text{As}_2\text{O}_5$ and $\text{Sr}_3\text{Sc}_{0.6}\text{Ti}_{1.4}\text{Fe}_2\text{As}_2\text{O}_5$, as shown in Fig. 3(d). Hence it raises one question: where does the superconductivity come from, “21113” phase, “32225” phase, or

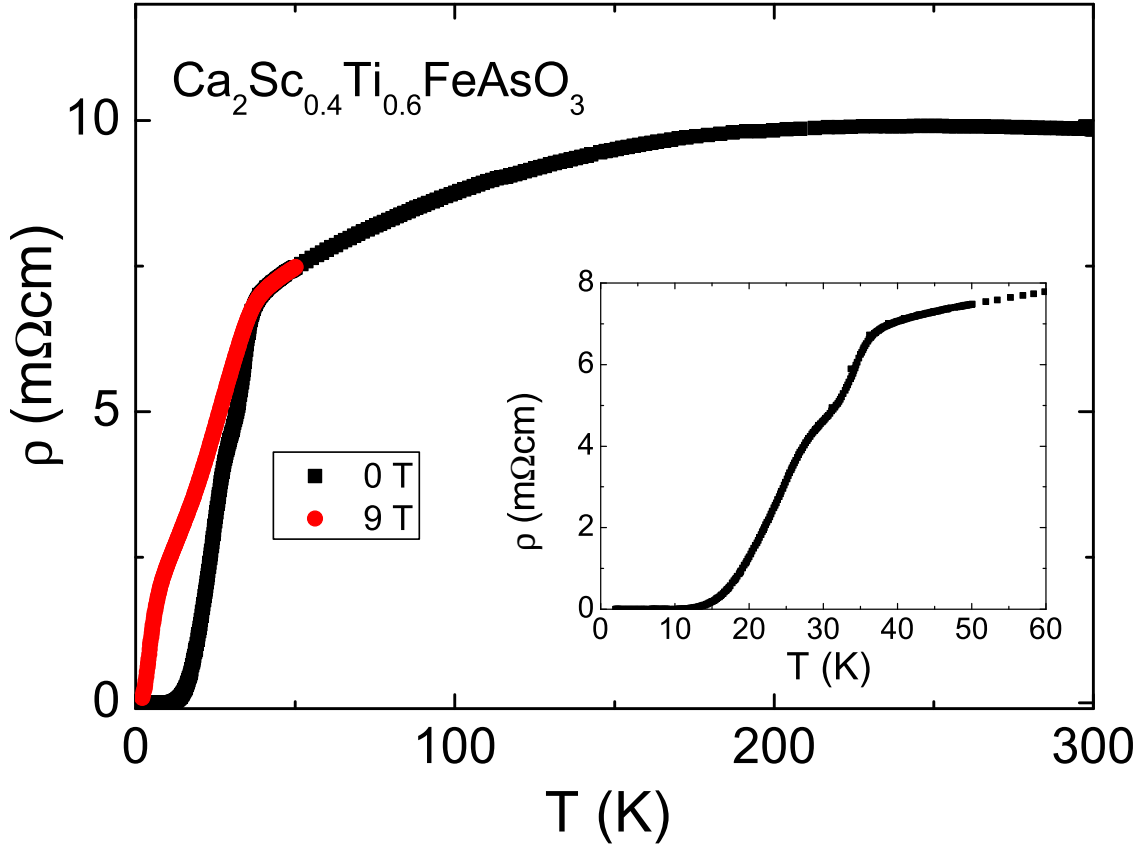


FIG. 4: (Color online) The electrical resistivity vs temperature for $\text{Ca}_2\text{Sc}_{0.4}\text{Ti}_{0.6}\text{FeAsO}_3$ under 0 T and 9 T. The inset shows the enlarged part at low temperature under 0 T.

other new phase? Detailed characterization of the superconducting phase is in progress.

Other members of this family with $A = \text{Ca}$ and Ba have also been prepared and characterized. Indeed, Ti ions doping in $\text{Ca}_2\text{ScFeAsO}_3$ can induce superconductivity with the onset temperature up to 37 K, as shown in Fig. 4. Up to now, no hint of superconductivity has been found in Ti-doped $\text{Ba}_2\text{ScFeAsO}_3$.

In summary, we have succeeded in preparing $\text{A}_2\text{ScFeAsO}_3$ ($A = \text{Ca}, \text{Sr}$) and performed a systematic study on effect of partial substitution of Sc^{3+} by Ti^{4+} in $\text{A}_2\text{ScFeAsO}_3$ and $\text{Sr}_3\text{Sc}_2\text{Fe}_2\text{As}_2\text{O}_5$ on the electrical properties. Superconductivity with the onset of T_c up to 45 K could be induced by high level electron doping. Our results indicate that it is possible to find high temperature superconductivity in other layered oxypnictides.

Acknowledgments

This work is supported by the NSFC, CAS, and the 973 project of the MOST of China.

-
- [1] Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono, *J. Am. Chem. Soc.* **130**, 3296 (2008)
 - [2] G.F. Chen, Z. Li, D. Wu, G. Li, W. Z. Hu, J. Dong, P. Zheng, J.L. Luo, and N.L. Wang, *Phys. Rev. Lett.* **100**, 247002 (2008)
 - [3] Z.-A. Ren, J. Yang, W. Lu, W. Yi, X.-L. Shen, Z.-C. Li, G.-C. Che, X.-L. Dong, L.-L. Sun, F. Zhou, and Z.-X. Zhao, *Europhys. Lett.* **82**, 57002 (2008)
 - [4] M. Rotter, M. Tegel, D. Johrendt, *Phys. Rev. Lett.* **101**, 107006 (2008)
 - [5] G. F. Chen, Z. Li, G. Li, W. Z. Hu, J. Dong, X. D. Zhang, P. Zheng, N. L. Wang, and J. L. Luo, *Chinese Phys. Lett.* **25**, 3403 (2008)
 - [6] M.S. Torikachvili, S.L. Bud'ko, N. Ni, P.C. Canfield, *Phys. Rev. Lett.*, **101**, 057006 (2008)
 - [7] X. C. Wang, Q. Q. Liu, Y. X. Lv, W. B. Gao, L. X. Yang, R. C. Yu, F. Y. Li, and C. Q. Jin, *Solid State Communications* **148**, 538 (2008).
 - [8] M. J. Pitcher, D. R. Parker, P. Adamson, S. J. C. Herkelrath, A. T. Boothroyd, and S. J. Clarke, *Chem. Commun.* 5918, (2008).
 - [9] J. H. Tapp, Z. J. Tang, B. Lv, K. Sasmal, B. Lorenz, C. W. Chu, and A. M. Guloy, *Phys. Rev. B* **78**, 060505 (2008).

- [10] F.C. Hsu, T.Y. Luo, K.W. Yeh, T.K. Chen, T.W. Huang, Phillip M.Wu, Y.C. Lee, Y.L. Huang, Y.Y. Chu, D.C. Yan, and M.K. Wu, Proc. Natl. Acad. Sci. USA. **105**, 14262 (2008).
- [11] I. R. Shein, A. L. Ivanovskii, arXiv:0903.4038
- [12] H. Ogino, Y. Matsumura, Y. Katsura, K. Ushiyama, S. Horii, K. Kishio, and J. -i. Shimoyama, arXiv:0903.3314
- [13] E. Brechtel, G. Cordier and H. Schafer, Z. Naturforsch **34**, 777 (1979)
- [14] W. J. Zhu and P. H. Hor, J. Am. Chem. Soc. **119**, 12398 (1997).
- [15] X. Y. Zhu, F. Han, G. Mu, P. Cheng, B. Shen, B. Zeng, and H. H. Wen, Phys. Rev. B **79**, 024516 (2009)